

Mechanical Properties of Hagfish Protein Hydrogels

Hayden Johns¹, Thomas Harris¹, Justin A Jones¹

Background

Hagfish are ancient animals that eject a strong slime when attacked by predators. This slime is composed of intermediate filaments that contribute to its incredible strength (Fig. 1 & Fig. 2).

To defend against foes, the Navy launches plastic ropes into the propellers of enemy warships in order to decrease the thrust of motors. In an effort to find a more biodegradable solution, the utilization of hagfish slime has shown great promise in stopping propellers (Fig. 3). We hope to understand how the slime withstands the impact of a quickly rotating propeller, while simultaneously reducing the propeller's thrust. What specific mechanical properties allow for this phenomena? From this research we can maximize the capabilities of this novel and versatile biomaterial.

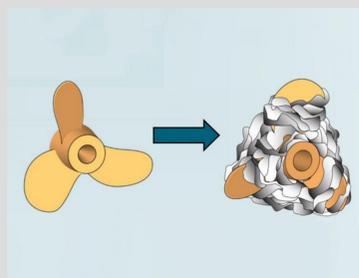
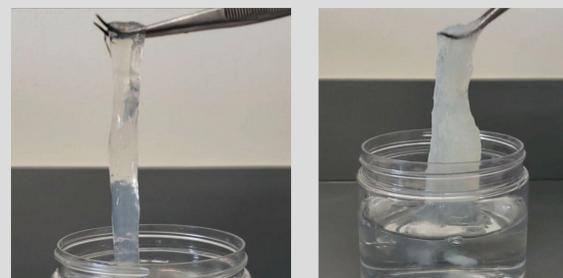


Fig. 1 (left): Recombinantly produced FW slime
Fig. 2 (right): Recombinantly produced SW slime

Fig. 3: Hagfish slime affecting a propeller

Methods

- Recombinantly produced alpha protein,, gamma protein,, or an equal mixture of the two are dissolved in formic acid at certain protein concentrations (10%, 15%, 20%, 25%)
- After 24 hrs, centrifuged and transferred to a syringe
- Extruded into strands in freshwater (FW) or a saltwater solution (SW)
- FW and SW slimes are tested in a tank of freshwater or saltwater
- Mechanically tested using the MicroTester from CellScale (Fig. 4 & Fig. 5) for force and elongation
- Analysis standardized by fiber diameter ($n \geq 10$)

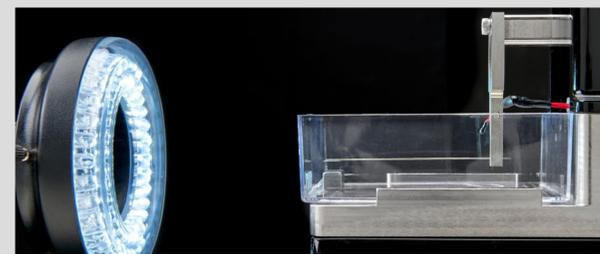


Fig. 4 CellScale MicroTester:
Strand secured horizontally and beam slowly compresses the fiber

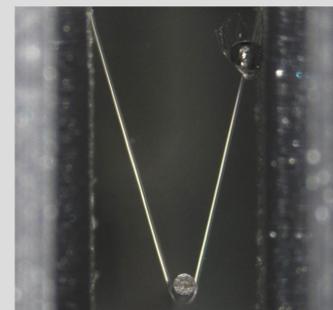


Fig. 5: Tension Test Example

Property	Concentration	Alpha				1:1 Alpha:Gamma				Gamma			
		FW-FW	FW-SW	SW-FW	SW-SW	FW-FW	FW-SW	SW-FW	SW-SW	FW-FW	FW-SW	SW-FW	SW-SW
Diameter (μm)	10%					114.2			136.1				
	15%	145.1	133	136.3	130	131.8	123.7	139.1	159	135.4	133.5	147.2	141.3
	20%					137.6			145				
	25%					143.1			153.3				
Stress (MPa)	10%					0.53			0.46				
	15%	0.78	0.78	1.96	1.64	0.99	0.65	1.05	0.84	0.66	0.42	0.59	0.66
	20%					1.06			1.38				
	25%					1.6			2.24				
Strain (mm/mm)	10%					2.41			4.15				
	15%	2.57	4.64	4.03	4.83	2.55	4.39	4.05	5.79	2.48	4.54	3.3	3.92
	20%					2.28			4.42				
	25%					2.47			4.97				
Toughness (MJ/m^3)	10%					0.57			1.06				
	15%	0.92	2.15	3.84	4.09	1.2	1.77	2.28	2.84	0.84	1.14	1.12	1.45
	20%					1.24			3.35				
	25%					2.01			6.2				
Elastic Modulus (kPa)	10%					204			225				
	15%	275	303	840	611	405	263	440	271	318	212	366	357
	20%					803			590				
	25%					1041			971				

Fig. 6: Results indicate alpha protein and higher protein concentration slime fibers outperform other fibers



¹ Hayden Johns; College of Science

Results

Initial results are indicated in Fig. 6. Key findings:

- FWW samples consistently performed the lowest for strain and toughness
- Diameters of fibers were fairly consistent across all conditions
- Higher protein concentration is positively correlated with higher stress, toughness and modulus, but had no apparent effect on strain
- Alpha fibers considerably outperform gamma fibers in terms toughness and stress
- Alpha fibers performed similarly, and occasionally outperform, mixed protein fibers- potential for lowered production

Future Work

Beyond replications using current methods, we hope to complete applied testing of well-performing fibers on propellers. Additionally, due to the known cytocompatibility, tunability, and mechanical characteristics of the fibers, which closely mimic native tissues, biomedical uses in tissue scaffolds are a viable research direction.